

*Georgiy Lisachuk, Olena Fedorenko, Oleg Pitak, Lyubov Bilostotska,
Yulia Trusova, Lyudmila Pavlova and Kateryna Dajneko*

THEORETICAL BACKGROUND OF ALKALINE-FREE TIN CONTENT COATINGS ON CERAMICS IN THE SYSTEM RO-SnO₂-Al₂O₃-SiO₂

*National Technical University "Kharkov Polytechnic Institute";
21, Frunze str., 61002 Kharkiv, Ukraine; Caterine@i.ua*

Received: October 29, 2012 / Revised: February 13, 2013 / Accepted: March 18, 2013

© Lisachuk G., Fedorenko O., Pitak O., Bilostotska L., Trusova Yu., Pavlova L., Dajneko K., 2013

Abstract. Theoretical calculations in the oxides systems RO-SnO₂-Al₂O₃-SiO₂, where RO – CaO, ZnO and BaO, have been done. Their structure has been established; eutectic and geometer-topological characteristics have been calculated. The process of the conodes adjustment at 1100 K has been revealed.

Keywords: systems, eutectic, geometer-topological characteristics, conodes adjustment.

1. Introduction

Recently in the technology of nonmetallic coatings for various purposes there has been a heightened interest in oxide of tin (IV) as a modifying component of glass matrix, which promotes a glass crystal structure due to the presence of valence electrons in shells s^2p^2 . SnO₂ oxide has specific features, namely, it provides glass resistance to alkalis and increases the melts viscosity to a lesser extent than ZrO₂ [1]. Its usage is known in the development of opaque vitreous and glass ceramic materials and coatings for ceramics, due to the high value of its own refractive index [2].

In multicomponent oxide alloys hexagonal coordination SnO⁴⁺ is more stable. SnO₂ is easily recovered from the alloy in the form of cassiterite crystals [3]. While using this oxide glasscrystal composition acquires a number of unique thermomechanical features: the rate of expansion decreases at the exchange of SiO₂ for SnO₂ and thin uniform crystallization is stimulated. It is one of the conditions for the creating a material with high heat resistance, density and structural strength. Introduction of CaO, ZnO and BaO to the glass composition significantly reduces the tin oxide solubility in molten glass and plays an important role in obtaining white opaque irrigated surfaces. Materials based on SnO₂, Al₂O₃, BaO, ZnO, CaO oxides and their compounds are of interest both in

the technology of special ceramic and refractory materials, and glass crystal materials technology.

The RO-SiO₂-Al₂O₃-B₂O₃-SnO₂ system (RO – oxides-modifiers among CaO, ZnO, BaO) was chosen as a basis for the investigations. Analysis of literature data has shown that the CaO-Al₂O₃-SnO₂, ZnO-Al₂O₃-SnO₂, BaO-Al₂O₃-SnO₂ systems were previously investigated insufficiently; some components of these systems are not yet studied substances [4, 5].

Thus, in order to predict the glass composition contents and their properties it is necessary to get information on the relationship of crystalline phases which are the part of the studied systems. It is a relevant and promising task of ceramics technology.

2. Experimental

Methods of the phase diagrams calculations correspond to those adopted in theoretical physico-chemical studies for multicomponent systems [6, 7]. To obtain the values of standard entropy S_{298}^0 we used Yatsymirsky method; the values of standard enthalpy ΔH_{298}^0 were calculated using Moraczewski and Sladkov method; the equation of heat capacity dependence on the temperature $C_p = f(T)$ [8, 9] was defined using Landiya method.

Modern thermodynamic data of the binary systems which form the researched three-components systems [10, 11] were involved as the initial data. The search showed that the available data on multicomponent tin-containing systems are very limited. Among the existing data on subsolidus status of the mentioned systems there is no information about alkaline-free tin-containing oxide systems with alkaline-earth oxide- [12-15].

In the literature there are data on the structure of two-component system Al₂O₃-SnO₂ [3], which is a simple eutectic system with the eutectic temperature of 1893 K. Eutectic is observed at 98 wt % SnO₂ and 1893 ± 5 K.

The small amounts of SnAl_2O_4 are formed while mixture quenching that indicates to the presence of a small proportion of SnO .

The binary system $\text{CaO-Al}_2\text{O}_3$ has been widely known in the technology of ceramics and carefully studied in the works of A. Berezhny [4]. The double phase diagrams of ZnO-SnO_2 , $\text{ZnO-Al}_2\text{O}_3$ and $\text{SnO}_2\text{-Al}_2\text{O}_3$ systems were investigated in the works [10, 12, 13]. It has been found out that $2\text{ZnO}\cdot\text{SnO}_2$ (Zn_2SnO_4) is formed in the first case and $\text{ZnO}\cdot\text{Al}_2\text{O}_3$ (ZnAl_2O_4) – in the second one. Stable compounds are not formed in the $\text{SnO}_2\text{-Al}_2\text{O}_3$ system.

3. Results and Discussion

The initial data for thermodynamic calculations were taken from [3, 7, 15, 16] and are listed in Table 1. Gibbs energy was calculated in the temperature range of 1073–1773 K with intervals of 50 K, taking into account the phase transition of alumina $\gamma\text{-Al}_2\text{O}_3 \rightarrow \alpha\text{-Al}_2\text{O}_3$.

Based on the literature data the $\text{CaO-Al}_2\text{O}_3\text{-SnO}_2$ system triangulation was done by plotting sections of all

possible pair interactions for this system. The probability of formation and coexistence of phases in the studied system was determined by the calculated values of Gibbs energy for the exchange reactions occurring in the temperature range of 600–1600 K. For the compounds $\text{CaO}\cdot\text{SnO}_2$ and $2\text{CaO}\cdot\text{SnO}_2$ only standard values of their enthalpy and entropy are known from the literature data [4-7]. In the absence of the heat capacity dependences on the temperature $C_p = f(T)$ their values were calculated in accordance with the method given in [6].

The diagram of the $\text{CaO-Al}_2\text{O}_3\text{-SnO}_2$ system and its topological graph are presented in Fig. 1. At the temperatures above 1100 K the changes of conodes structure take place, namely, the formation of such elementary triangles, the ratio between which can be described by the phase diagram and topological graph of the following view (Fig. 1). The coincidence of both graphs indicates the same interaction character in the system between its constituent phases and shows no complex phase transitions and unstable compounds.

Table 1

Thermodynamic constants of compounds

Compound formulas	Melting point, K	$-\Delta f^0_{298}$, kcal/mol	S^0_{298} , cal/mol·grad	$C_p = f(T)$		
				a	$b \cdot 10^3$	$c \cdot 10^{-5}$
CaO-Al₂O₃-SnO₂						
CaO	2898	151.9	9.5	11.67	1.08	-1.56
$\alpha\text{-Al}_2\text{O}_3$	2327	400.48	12.17	27.43	3.06	-8.47
$\text{CaO}\cdot 6\text{Al}_2\text{O}_3$	1903	2549.4	73.8	138.736	96	-5.311
$\text{CaO}\cdot 2\text{Al}_2\text{O}_3$	2123	957.06	42.5	66.09	5.48	-17.8
$\text{CaO}\cdot \text{Al}_2\text{O}_3$	2038	556.18	27.3	36.01	9.98	-7.26
$12\text{CaO}\cdot 7\text{Al}_2\text{O}_3$	1878	4640.16	249.7	301.96	65.5	-55.3
$3\text{CaO}\cdot \text{Al}_2\text{O}_3$	1729	851	49.1	62.28	4.58	-12.09
SnO_2	1808	138.3	12.5	17.66	2.4	-5.16
$\text{CaO}\cdot \text{SnO}_2$	2073	305.2	18.6	26.574	5.246	-2.963
$2\text{CaO}\cdot \text{SnO}_2$	2073	456.6	28.8	35.978	7.774	-1.044
ZnO-Al₂O₃-SnO₂						
ZnO	2248	348.48	44.0	49.06	5.11	-9.13
$\alpha\text{-Al}_2\text{O}_3$	2327	400.48	12.17	27.43	3.06	-8.47
SnO_2	1903	579.48	52.375	74.0	10.06	-21.62
$2\text{ZnO}\cdot \text{SnO}_2$	2211	3197.14	150.25	82.83	206.93	15.64
$\text{ZnO}\cdot \text{Al}_2\text{O}_3$	2223	2069.86	100.31	427.38	355.73	-
BaO-Al₂O₃-SnO₂						
BaO	2193	558.15	70.29	53.3	4.35	-8.3
$\alpha\text{-Al}_2\text{O}_3$	2327	1675.61	50.92	114.77	12.08	-35.44
SnO_2	1903	579.48	52.375	74.0	10.06	-21.62
$\text{BaO}\cdot \text{SnO}_2$	2333	3260.15	146.52	39.40	202.47	16.02
$2\text{BaO}\cdot \text{SnO}_2$	2183	3678.65	159.64	78.37	219.24	17.01
$\text{BaO}\cdot \text{Al}_2\text{O}_3$	2088	2334.17	123.43	148.32	35.44	-29.25
$3\text{BaO}\cdot \text{Al}_2\text{O}_3$	2188	3537.91	267.78	247.86	48.53	-17.41
$\text{BaO}\cdot 6\text{Al}_2\text{O}_3$	1893	10740.33	376.56	738.22	70.5	-221.75
$4\text{BaO}\cdot \text{Al}_2\text{O}_3$	1873	4014.49	329.99	275.85	56.89	-23.33
$8\text{BaO}\cdot \text{Al}_2\text{O}_3$	1923	6238.10	611.68	441.99	96.23	-25.31

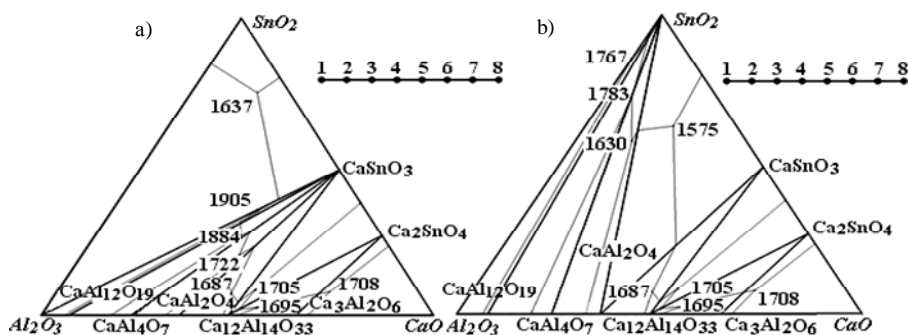


Fig. 1. Phase diagram and topological graph of the CaO-Al₂O₃-SnO₂ system: temperatures below 1100 K (a) and temperatures above 1100 K (b)

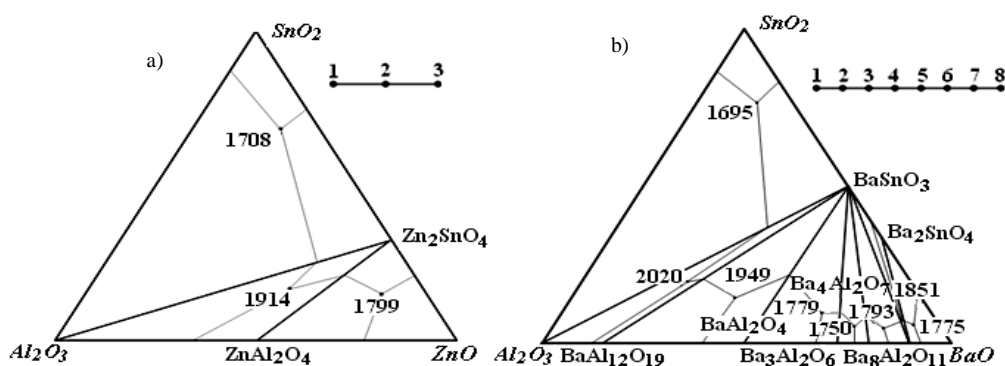


Fig. 2. Phase diagram and topological graph of the systems ZnO-SnO₂-Al₂O₃ (a) and BaO-SnO₂-Al₂O₃ (b)

To triangulate the ZnO-SnO₂-Al₂O₃ and BaO-SnO₂-Al₂O₃ systems we calculated enthalpy, entropy and constants of heat capacity dependence on temperature for zinc stannate and barium stannate (Zn₂SnO₄, BaSnO₃ and Ba₂SnO₄), as well as entropy values for ZnO·Al₂O₃.

As a result of investigations the subsolidus structure of ZnO-SnO₂-Al₂O₃ and BaO-SnO₂-Al₂O₃ system was determined. Its phase diagram is represented in Fig. 2a.

We did not find the information about the structure of the BaO-SnO₂-Al₂O₃ system. Data retrieval concerning the two-component systems [17] has shown that two compounds are formed in the BaO-SnO₂ system: BaO·SnO₂ (BaSnO₃) and 2BaO·SnO₂ (Ba₂SnO₄). There is also information about the existence of 3BaO·SnO₂ (Ba₃Sn₂O₇) compound but its formation is possible only under special conditions, that is why during the triangulation it was not taken into account.

Among 8 barium-aluminate compounds which may be formed in this two-component system at the triangulation in the BaO-SnO₂-Al₂O₃ system we consider only phases stable at 1673 K: BaAl₂O₄, Ba₃Al₂O₆, BaAl₁₂O₁₉, Ba₄Al₂O₇ and Ba₈Al₂O₁₁. As it was mentioned above, in the system SnO₂-Al₂O₃ the stable compounds are absent.

Taking these data into account the triangulation for three-component BaO-SnO₂-Al₂O₃ system also was done using the calculation method. On the basis of literature data the conodes sections characterizing all possible pair interactions in this system were plotted. Diagram and topological graph of the BaO-SnO₂-Al₂O₃ system as a result of triangulation is represented in Fig. 2b. It gives some information about the conodes location and phase interaction. The geometric-topological characteristics and eutectics of elementary triangles obtained as a result of triangulation are represented in Table 2.

The information about the structure of oxide systems containing SnO₂ is very limited. But it is needed to analyze the behavior of oxide compositions at heating in the process of thermal treatment of materials. The investigation of alkaline-earth oxides effect on phase formation in tin-containing oxide compositions is of great importance, because they significantly affect the processes of crystallization and glass formation [18].

4. Conclusions

As a result of theoretical studies the location of elementary triangles in the experimental systems has been established, their geometric-topological characteristics and

eutectics parameters have been specified. The data have been used to determine the oxide compositions field in the in the CaO-BaO-ZnO-SnO₂-Al₂O₃-SiO₂ system.

Table 2

The eutectics composition and temperature

Elementary triangle	Eutectics composition, mas %			Eutectics temperature, K
Al ₂ O ₃ -SnO ₂ -CaO system				
Temperatures below 1100 K	Al ₂ O ₃	SnO ₂	CaO	
Al ₂ O ₃ -SnO ₂ -CaSnO ₃	22.28	65.58	12.14	1637
Al ₂ O ₃ -CaAl ₁₂ O ₁₉ -CaSnO ₃	63.04	26.68	10.28	1905
CaAl ₁₂ O ₁₉ -CaAl ₄ O ₇ -CaSnO ₃	63.14	23.39	13.47	1884
CaAl ₄ O ₇ -CaAl ₂ O ₄ -CaSnO ₃	39.48	38.80	21.72	1722
CaAl ₂ O ₄ -Ca ₁₂ Al ₁₄ O ₃₃ -CaSnO ₃	43.34	15.81	40.85	1687
Ca ₁₂ Al ₁₄ O ₃₃ -Ca ₂ SnO ₄ -CaSnO ₃	35.96	22.44	41.60	1705
Ca ₁₂ Al ₁₄ O ₃₃ -Ca ₃ Al ₂ O ₆ -Ca ₂ SnO ₄	42.93	7.78	49.29	1695
Ca ₃ Al ₂ O ₆ -Ca ₂ SnO ₄ -CaO	17.45	25.39	57.16	1708
Temperatures above 1100 K				
Al ₂ O ₃ -SnO ₂ -CaAl ₁₂ O ₁₉	77.15	16.31	6.54	1767
CaAl ₁₂ O ₁₉ -SnO ₂ -CaAl ₄ O ₇	75.20	13.92	10.88	1783
CaAl ₄ O ₇ -SnO ₂ -CaAl ₂ O ₄	53.78	26.41	19.81	1630
CaAl ₂ O ₄ -SnO ₂ -CaSnO ₃	15.47	67.82	16.71	1575
CaAl ₂ O ₄ -Ca ₁₂ Al ₁₄ O ₃₃ -CaSnO ₃	43.34	15.81	40.85	1687
Ca ₁₂ Al ₁₄ O ₃₃ -Ca ₂ SnO ₄ -CaSnO ₃	35.96	22.44	41.60	1705
Ca ₁₂ Al ₁₄ O ₃₃ -Ca ₃ Al ₂ O ₆ -Ca ₂ SnO ₄	42.93	7.78	49.29	1695
Ca ₃ Al ₂ O ₆ -Ca ₂ SnO ₄ -CaO	17.45	25.39	57.16	1708
ZnO-SnO ₂ -Al ₂ O ₃ system				
	ZnO	SnO ₂	Al ₂ O ₃	
SnO ₂ -Al ₂ O ₃ -Zn ₂ SnO ₄	27.99	53.79	18.22	1708
Al ₂ O ₃ -Zn ₂ SnO ₄ -ZnAl ₂ O ₄	40.07	25.39	34.54	1914
Zn ₂ SnO ₄ -ZnAl ₂ O ₄ -ZnO	55.74	26.30	17.96	1799
BaO-SnO ₂ -Al ₂ O ₃ system				
	BaO	SnO ₂	Al ₂ O ₃	
Al ₂ O ₃ -SnO ₂ -BaSnO ₃	27.55	54.13	18.32	1695
Al ₂ O ₃ -BaAl ₁₂ O ₁₉ -BaSnO ₃	26.04	12.99	60.97	2020
BaAl ₁₂ O ₁₉ -BaSnO ₃ -BaAl ₂ O ₄	34.59	11.48	53.93	1949
BaSnO ₃ -BaAl ₂ O ₄ -Ba ₃ Al ₂ O ₆	67.81	13.56	18.63	1779
BaSnO ₃ -Ba ₃ Al ₂ O ₆ -Ba ₄ Al ₂ O ₇	76.40	9.62	13.98	1750
BaSnO ₃ -Ba ₄ Al ₂ O ₇ -Ba ₈ Al ₂ O ₁₁	84.10	6.50	9.40	1793
BaSnO ₃ -Ba ₈ Al ₂ O ₁₁ -Ba ₂ SnO ₄	80.60	14.30	5.10	1851
Ba ₈ Al ₂ O ₁₁ -Ba ₂ SnO ₄ -BaO	86.97	7.55	5.48	1775

The calculations of necessary thermodynamic constants ($C_p = f(T)$) have been done, phase diagrams of oxide systems have been plotted and the eutectics parameters in ternary diagrams have been defined.

The eutectic temperatures increased depending on oxide in such a sequence: CaO-ZnO-BaO. The phase diagrams show the lowest temperature of eutectics relates

to the elementary triangles with enhanced content of SnO₂. Two other components formed chain-like bonds. Most of the bonds for CaO and BaO have been found. The obtained theoretical correlation of oxide ratio can be used for design of opaque tin-containing coatings with enhanced density and heat-resistance in the CaO-BaO-ZnO-SnO₂-Al₂O₃-SiO₂ system.

References

- [1] Appen A.: Khimija Stekla. Khimija, Leningrad 1974.
- [2] Nikol'skij B.: Spravochnik Khimika. Khimija, Leningrad 1971.
- [3] Bobkova N., Kuz'menkova N. and Bogdanovich I.: Steklo i Keramika, 2008, **6**, 32.
- [4] Toropov N., Barzakovskij V., Lapin V. et al.: Diagrammy Sostojanija Silikatnyh System. Nauka, Leningrad 1972.
- [5] Barzakovskij V. et al.: Diagrammy Sostojanija Silikatnyh System. Nauka, Moskva 1974.
- [6] Berezhnyj A., Pitak Ja., Ponomarenko O. and Sobol' N.: Fizyko-Khimichni Systemy Tugoplavkykh Nemetallichnykh i Sylikatnykh Materialiv. NMK VO, Kyiv 1992.
- [7] Babushkin V.: Termodinamika Silikatov. Strojizdat, Moskva 1986.
- [8] Morachevskij A.: Termodinamicheskie Raschety v Metallurgii. Metallurgija, Moskva 1985.
- [9] Landiya N.A. Raschet Vysokotemperaturnykh Teployemkostey Tverdyykh Neorganicheskyykh Veshchestv po Standartnoy Entropiyi.: Izd-vo AN GruzSSR, Tbilisi 1962.
- [10] Galahov F.: Diagrammy Sostojanija System Tugoplavkikh Oksidov. Nauka, Leningrad 1985.
- [11] Berezhnoj A.: Mnogokomponentnye Systemy Okislov. Naukova dumka, Kiev 1970.
- [12] Barchak V. and Insly R.: J. Am. Ceram. Soc., 1962, **45**, 144.
- [13] Roth R.: National Bureau of Standards, Gaithersburg, Maryland 1987.
- [14] Cadee M. and Ijdo D.: J. Solid State Chem., 1981, **36**, 314.
- [15] Chuhrov F., Ostrovskij I. and Lapin V.: Mineraly. Diagrammy Phazovykh Ravnovesij. Nauka, Moskva 1974.
- [16] Glushko V., Medvedev V. et al.: Termicheskie Konstanty Veshchestv. VINITI, Moskva 1970.
- [17] Shabanova G.: Barijsoderzhashchie Oksidnye Systemy i Vjzhashchchie Materialy na ikh Osnove. NTU "KHPI", Kharkov 2006.
- [18] Lisachuk G., Pitak O., Tsovm V. et al. Visnyk Nats. Techn. Univ. «Kharkivskiy Politehnichnyj Instytut», 2011, **27**, 102.

ТЕОРЕТИЧНІ ОСНОВИ БЕЗЛУЖНИХ ОЛОВОМІСНИХ ПОКРИТТІВ ПО КЕРАМІЦІ В СИСТЕМІ RO-SnO₂-Al₂O₃-SiO₂

Анотація. Проведено теоретичні розрахунки в системах оксидів RO-SnO₂-Al₂O₃-SiO₂, де RO – CaO, ZnO та BaO, встановлена їх будова, розраховані евтектики та геометро-топологічні характеристики. В залежності від перебудови конод за температури 1100 K виявлено можливості застосування складів композицій в різних технологіях.

Ключові слова: система, евтектика, геометро-топологічні характеристики, перебудова конод.